

# 1

*by* Lova Lova

---

**Submission date:** 08-May-2023 03:10PM (UTC+0700)

**Submission ID:** 2087356682

**File name:** JURNAL\_Q3.pdf (1.39M)

**Word count:** 4492

**Character count:** 21932

# 1 Stainless 37 Steel Corrosion Inhibition in a Hydrochloric Acid Solution with Senggani (*Melastoma Candidum D. Don*) Leaf Extract

L. Anggraini<sup>1\*</sup>, Emriadi<sup>2</sup>, Y. Stiadi<sup>2</sup>, S. Zulaiha<sup>3</sup> and H. Pardi<sup>4</sup>

<sup>1</sup>Faculty of Pharmacy and Health Sciences, Abdurrah Pekanbaru University,  
Riau, Indonesia

<sup>2</sup>Faculty of Mathematics and Natural Sciences, Andalas University, Padang, Indonesia  
<sup>3</sup>Faculty of Animal Science and Agriculture, University Islam Negeri Sultan Syarif Kasim  
Riau. Jl. HR. Soebrantas Km. 15, Tuah Karya, Tampan, Kampar 28293, Riau, Indonesia

<sup>4</sup>Department of Chemistry Education, Faculty of Teacher Training and Maritim  
Education, Raja Ali Haji University, Senggarang, Tanjungpinang 29111, Indonesia

\*Corresponding author: loveraanggraini@univrab.ac.id

Received 07/11/2021; accepted 01/03/2022  
<https://doi.org/10.4152/pea.2023410302>

## Abstract

SLE (*Melastoma candidum D. Don*) was tested as an inhibitor of St-37 S corrosion in a HCl solution, using WL, PDP and SEM analysis methods. CR has decreased with SLE addition, according to the WL method. The highest IE(%) was 67%, with 0.8% SLE addition. Rise in T had a decreasing effect on IE(%). PDP showed that the extract was a mixed inhibitor. SEM analysis showed changes in the St-37 S surface immersed in HCl, without and with the inhibitor. SLE adsorption onto the steel surface obeyed Langmuir's isotherm.

**Keywords:** corrosion IE(%), Langmuir's isotherm, PDP, SEM, SLE, St-37 S and WL.

## Introduction\*

Steel is a versatile material, with several applications in industry, automobiles and construction. When steel gets in contact with the environment or aggressive substances like acids, it undergoes corrosion, which is a natural process that hinders materials performance and causes losses that are a major issue in industry.

Therefore, it is necessary to deal with the corrosion effects. One way to prevent them is to add corrosion inhibitors that protect metals surfaces against acids, by decreasing the anodic oxidation and cathodic reduction rates, or both.

The inhibitors form a protective film on the metal surface by physical (electrostatic) adsorption or chemisorption [1-6].

\* The abbreviations and symbols definition lists are in pages 207 and 208.

Corrosion inhibitors can be composed of inorganic or organic materials. Surfactants, polymers and substances containing O, N, S, P and aromatic compounds, as well as double bonds, are all examples of organic molecules that can be employed as inhibitors [6-11].

Despite the fact that MS easily rusts in humid air and has a high CR in extremely acidic environments, it is one of the most commonly used technical materials for automotive constructions and applications. Thus, MS corrosion resistance is critical. In addition to the standard processes, chemical inhibitors are an alternative way of preventing corrosion in acidic solutions [12-15].

Senggani is one of the plants that grows in Indonesia. Its leaves contain saponins, flavonoids and tannins. These organic chemicals are intended to be adsorbed onto the steel surface, reducing and maybe preventing corrosion [2,8].

Therefore, this research has been carried out with the aim of determining St-37 S CR in a HCl solution with or without SLE, and studying the metal changes by SEM analysis.

## **Materials and methods**

### ***St-37 S surface preparation***

St-37 S bars were cut in coupons with a diameter of  $24 \pm 2.5$  cm and a thickness of  $\pm 0.1$  cm. Their surface was smoothed by Fe sandpaper, and rinsed with distilled water. Then, they were cleaned with acetone, to remove any grease that might have adhered to them. Furthermore, they were dried in an oven, at a T of 60 °C. Afterwards, the St-37 S coupons were weighed, and the results were expressed as  $m_1$ .

### ***SLE preparation***

SL were taken in the area surrounding the Andalas University forest. Only the green SL were taken, freshly dried, mashed, weighed up to 400 g, and extracted thrice with 2000 mL CH<sub>3</sub>OH, where they were kept for 3 days. The obtained extract was filtered, and the solvent was evaporated using a rotary evaporator (Heidolph W2000). The obtained concentrated SLE was placed into a 100 mL glass beaker, to make a solution with different C (0, 0.2, 0.4, 0.6 and 0.8%).

### ***SLE phytochemical screening***

SLE phytochemical screening was done to qualitatively determine the presence of flavonoids, triterpenoids, steroids and phenolic compounds, using the following method: 1 g of the SLE sample was put into a test tube, and macerated with CH<sub>3</sub>OH that had been heated (on a water bath) for 15 min. Then, it was filtered hot into another test tube, and all the CH<sub>3</sub>OH was let to be evaporated.

Afterwards, 5 mL each CHCl<sub>3</sub> and water were added to the sample in a ratio of 1:1. The mixture was well shaken, transferred into a test tube, and left for a moment, until two layers of CHCl<sub>3</sub>-H<sub>2</sub>O were formed.

The CHCl<sub>3</sub> layer at the bottom and the H<sub>2</sub>O layer were used for examining triterpenoid and steroids, and phenolic and flavonoids, respectively.

*Tests for flavonoids, phenolic, triterpenoids and steroids, and alkaloids compounds*

Tests were made for the detection of the following compounds: for flavonoids, some of the H<sub>2</sub>O layer was taken and transferred with a pipette into a test tube. Then, concentrated HCl and a few grains of Mg powder were added to it. The change in color of orange to red indicated their presence; for phenolics, a portion of the H<sub>2</sub>O layer was put by a pipette into a test tube. Then, FeCl<sub>3</sub> was added to it. Blue coloration indicated their presence; for steroids and triterpenoids, a drop each of acetic anhydride and concentrated H<sub>2</sub>SO<sub>4</sub> were put into a hole plate from the CHCl<sub>3</sub> layer. The appearance of green or blue, and red colors, respectively, indicated their presence; finally, for alkaloids, 2-4 g of the sample were cut into little pieces, crushed in a mortar with sand and 10 mL of 0.05 N CHCl<sub>3</sub>-NH<sub>3</sub>, and then slowly agitated or ground. The solution was filtered through a small funnel with a cotton swab, and the filtrate was transferred into a test tube, where 10 drops of 2 N H<sub>2</sub>SO<sub>4</sub> were added and gently shaken, for a few moments, until NH<sub>3</sub> and CHCl<sub>3</sub> layers were separated. With a pipette, NH<sub>3</sub> layer was removed and put into a tube. Then, Meyer's reagent was added. The appearance of a white precipitate indicated their presence.

***HCl corrosive medium preparation***

103.5 mL of a 37% HCl solution were pipetted and put it into a 250 mL volumetric flask that already contained distilled H<sub>2</sub>O. Furthermore, distilled H<sub>2</sub>O was added up to the limit mark. The obtained 5 N HCl solution was used to prepare the HCl corrosive medium. The prepared steel was immersed into the pipetted 10 mL HCl solutions that were used for the tests.

***HCl corrosive medium preparation with SLE***

SLE with different C (0, 0.2, 0.4, 0.6 and 0.8%) was mixed with 10 mL of the 1.0 N HCl solution. Then, distilled H<sub>2</sub>O was added until the volume was 50 mL.

***CR based on the WL method***

St-37 S was immersed in 50 mL of the 1 N HCl solution, at various C, with and without SLE, at T of 30, 40, 50 and 60 °C, for 7 h, using a water bath. The steel was then cleaned, rinsed and dried in the oven, at 60 °C. After drying, St-37 S was weighed, and the findings were expressed as m<sub>2</sub>.

***PDP method***

In PDP measurements, St-37 S (with a diameter of 2.54 cm and a surface area of 0.020 cm<sup>2</sup>), Pt and Ag/AgCl were used as WE, AE and RE, respectively. The three electrodes were immersed in a vessel containing HCl without and with 0, 0.2, 0.4, 0.6 and 0.8% SLE. Then, they were connected to a potentiostat, and E was adjusted, so that the curve of the relationship between E vs I was obtained. In the PDP measurements, the curve of the relationship between E (mV) and current log (mA/cm<sup>2</sup>) was obtained. E was set from -1000 to 500 mV, in order to obtain a PDP curve [14-17].

### FTIR spectroscopy

FTIR (Thermo Scientific Nicolet iS10) analysis was carried out by measuring the corrosion of St-37 S, and washing, drying and analyzing the metal, using a KBr pellet plate. FTIR analyses were also carried out for SLE.

### SEM

St-37 S was immersed in 1 N HCl, without and with SLE, for 7 h. Then, it was dried and analyzed by SEM (Hitachi S-3400N).

## Results and discussion

### Phytochemical screening

The presence or absence of alkaloids, flavonoids, phenolics and triterpenoids compounds in SLE was determined by phytochemical screening. The + and - signs indicate them in Table 1.


**Table 1.** Phytochemical screening results on SLE.

Phytochemical screening	SLE
Alkaloids	+
Flavonoids	++
Phenolic	+
Triterpenoid	+
Steroids	-

### SLE corrosion IE(%) evaluation by WL

#### C effect on St-37 S CR with T variations

Fig. 1 shows SLE C (0 to 0.8%) effect on St-37 S CR in 1 N HCl. CR decreased as SLE content increased. It was only 0.78 mg/cm<sup>2</sup>/h with 0.8% SLE.

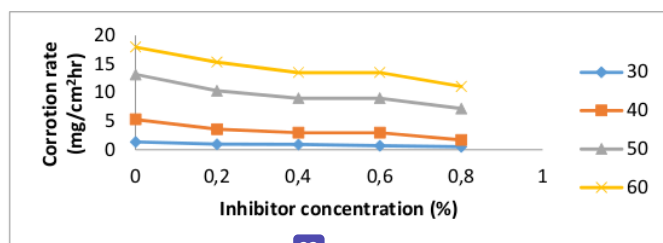


**Figure 1.** SLE C effect on CR of St-37 S immersed for 7 h in a 1 N HCl solution.

### St-37 S CR IE(%) by SLE

Fig. 2 shows IE(%) with different SLE C. As SLE C was increased, its IE(%) also rose, reaching 67% at 0.8% in 1 N HCl medium. The stronger SLE adsorption onto the St-37 S surface resulted in the formation of a thin layer that protected the metal, resulting in a decrease in CR and an increase in IE(%) [18-19]. SLE acted as a ligand, because of its lone pair of electrons donated to the Fe<sup>3+</sup> center. This compound


complex protected St-37 S from HCl attack. The protective layer inhibited aggressive ions from reaching the metal, reducing its CR in HCl [18-20].

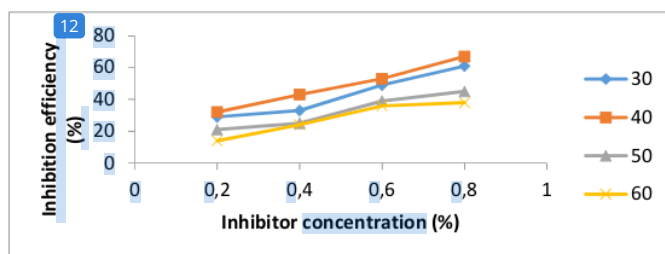

**Figure 2.** SLE C effect on its IE(%) for St-37 S corrosion in a 1 N HCl solution, at different T, for 7 h.

*E<sub>a</sub> determination*

The St-37 S CR value in 1 N HCl without and with SLE, at various T of 30, 40, 50 and 60 °C, was used to determine E<sub>a</sub>. The relationship between 1/T and ln V produced a straight line, as shown in Fig. 3 graph. The slope value was E<sub>a</sub>/2.303 R.

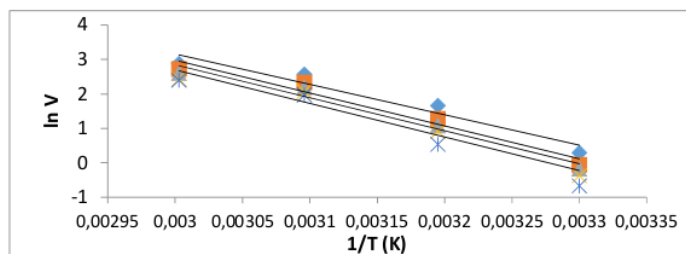

**Figure 3.** Arrhenius flow (1/T (K<sup>-1</sup>) vs ln V) for St-37 S CR in 1 N HCl, with an immersion time of 7 h.

Table 2 shows that E<sub>a</sub> with SLE was higher than without it. The high E<sub>a</sub> suggests that the reaction was difficult to initiate, due to the layer formed by SLE adsorption onto St-37 S. This layer protected the metal against HCl attack and corrosion [20-26].

**Table 2.** E<sub>a</sub>, ΔH° and entropy ΔS° values without and with SLE.

Medium	E <sub>a</sub> (kJ/mol)	ΔH° (kJ/mol)	ΔS° (kJ/mol)
1 N HCl	73.38	29.70	82.61
1 N HCl + 0.2 % SLE	79.36	30.99	77.81
1 N HCl + 0.4% SLE	79.73	48.19	27.46
1 N HCl + 0.6% SLE	80.95	50.47	20.02
1 N HCl + 0.8% SLE	89.76	51.17	17.71

$\Delta H^\circ$  value was positive, indicating that the occurred process was an endothermic reaction.  $\Delta H^\circ$  value of a reaction with an inhibitor is higher than without it. This demonstrates that the corrosion process requires a significant amount of energy.  $\Delta S^\circ$  value with various SLE C was also higher than without the inhibitor. This demonstrates that adding inhibitors to metals slows down the corrosion process.

#### SLE corrosion IE(%) analysis by the adsorption isotherm method

Fig. 4 shows an adsorption isotherm based on the WL method analysis that follows the Langmuir's adsorption isotherm, because the path between C and C/θ gave a straight line, with a R<sup>2</sup> of 0.9126.

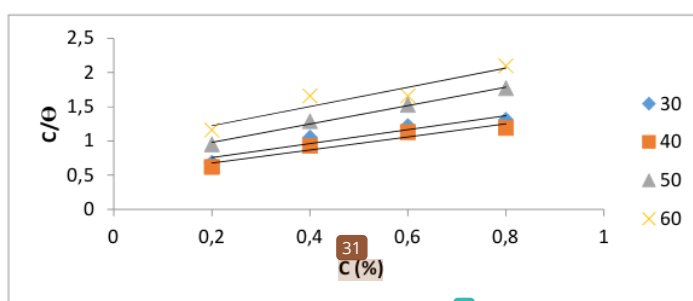


Figure 4. Langmuir's adsorption isotherm for St-37 S corrosion in 1 N HCl, for 7 h of immersion time, based on the WL method.

$K_{ads}$  and  $\Delta G_{ads}$  values for SLE adsorption on the St-37 S surface shown in Table 3. The inhibitor adsorption onto the steel surface was considered physisorption, if the  $\Delta G$  value was greater than -20 kJ/mol. The inhibitor and steel had a weak bond in this kind of absorption, which caused the complex between them to be easily dissociated.


Table 3.  $K_{ads}$  and  $\Delta G_{ads}$  values, at T from 30 to 60 °C.

Temperature (°C)	$K_{ads}$ (mmol <sup>-1</sup> )	$\Delta G_{ads}$ (kJ/mol)
30	1.818	-11.623
40	2.040	-12.306
50	1.408	-11.703
60	1.063	-11.287

#### SLE corrosion IE(%) analysis by PDP method

Fig. 5 indicates that the reactions occurred with both anodic and cathodic processes, based on extrapolated data from the Tafel plot. SLE inhibited anodic corrosion by its adsorption, which inhibited the oxidation reaction or reduced the metal solubility. SLE also inhibited cathodic corrosion by the reaction between it and HCl H<sup>+</sup> ions, which mitigated the reduction process of H<sup>+</sup> ions into H<sub>2</sub>.  $E_{corr}$  value changed towards anodic and cathodic directions. Its value that went up and down indicates the stability

of SLE adsorption onto the St-37 S surface.  $I_{corr}$  was caused by the movement of oxidized metal electrons in the HCl medium [27-34].

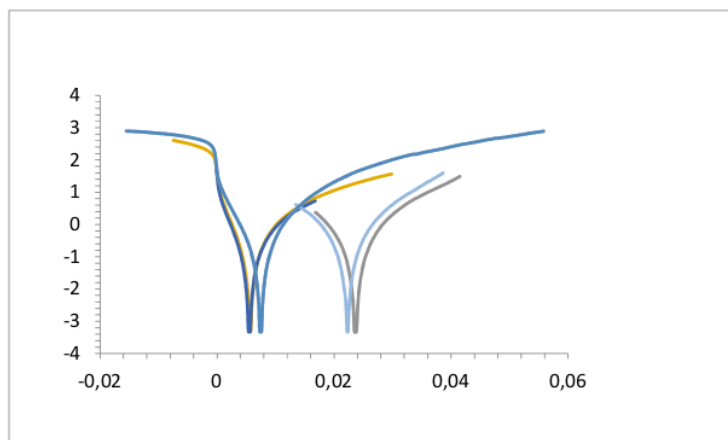

**Figure 5.** PDP curve without and with SLE in the 1 N HCl solution.

Table 4 shows that, when SLE C were increased,  $I_{corr}$  values fell. The decrease in  $I_{corr}$  was caused by SLE, because the electrons movement of the oxidized St-37 S in 1 N HCl decreased. With higher SLE C, IE(%) increased. The highest IE(%) (69.72%) was obtained from the extrapolated Tafel slope value with SLE addition at a C of 0.8%.


**Table 4.**  $E_{corr}$ ,  $I_{corr}$ , IE(%) and extrapolated Tafel plots values without and with SLE.

SLE C	$E_{corr}$ (V)	$I_{corr}$ ( $\mu\text{A}/\text{cm}^2$ )	IE (%)
0	0.0068	0.0182	-
0.2	0.0268	0.00913	49.83
0.4	0.0632	0.00872	52.08
0.6	0.0243	0.00774	57.47
0.8	0.0523	0.00551	69.72

### FTIR analysis

FTIR spectrum of 0.5% SLE and corrosion products (rust) from St-37 S <sup>10</sup>immersion in 1 N HCl, for 7 h, at 30 °C, is shown in Fig. 6. Fig. 6a shows SLE spectrum, which contains the hydroxyl group of -OH (3500-3000  $\text{cm}^{-1}$ ), CH (3000-2500  $\text{cm}^{-1}$ ), C = C (1640-1610  $\text{cm}^{-1}$ ), and CO (1042-1448  $\text{cm}^{-1}$ ) stretchings, and a low  $\text{CO}_2$  vibration intensity peak at wave number 2360.37  $\text{cm}^{-1}$ . In Fig. 6b, there is a shift in -OH from the wave number 3393.75 to 3432.19  $\text{cm}^{-1}$ , a shift in the C=C stretching group from the wave number 1616.78  $\text{cm}^{-1}$  to 1637.66  $\text{cm}^{-1}$ , and a shift in the other functional groups. This tended to happen when SLE interacted with the St-37 S surface, forming a thin protective layer.




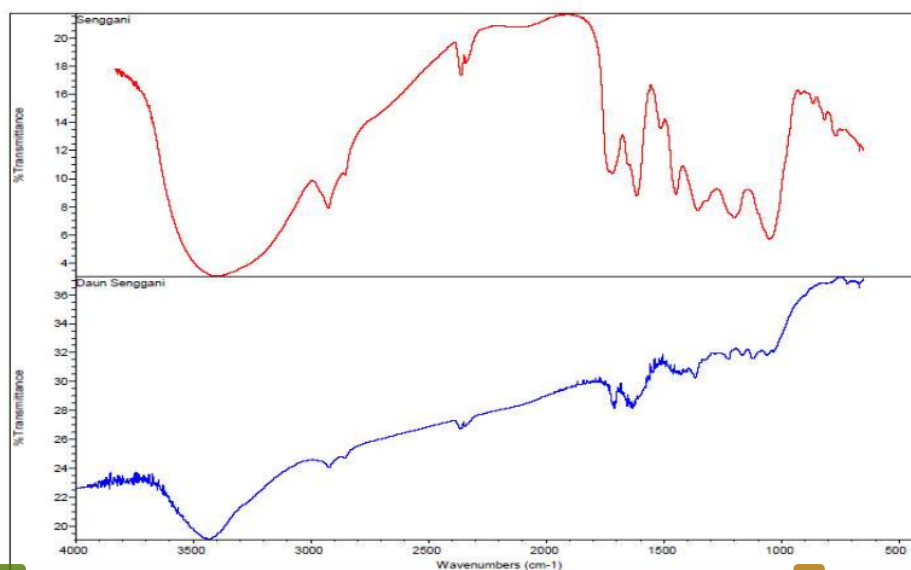

10 **Figure 6.** FTIR spectra of (a) SLE and (b) corrosion products from St-37 S immersion in 1 N HCl with SLE, for 7 h. 18

### SEM analysis

28 Fig. 7 shows that there was no damage caused by SLE presence. This was due to the SLE adsorption on the St-37 steel surface, which formed a protective coating that protected the metal and caused it to corrode only slightly. Fig. 7 (a) shows the St 37 S surface without treatment, at 100 x magnification. The metal surface still looks good, not porous, and did not crack, because there was no interaction with HCl. Fig. 7 (b) shows the steel surface after 7 h of immersion in HCl. Corrosion caused obvious holes and brownish rust on the metal surface, due to its interaction with H<sup>+</sup> and Cl<sup>-</sup> ions. Fig. 7 (c) shows St-37 S surface immersed in HCl with 0.5% SLE, revealing that it was less damaged than the one without it, because the inhibitor formed a protective layer on the metal. 25

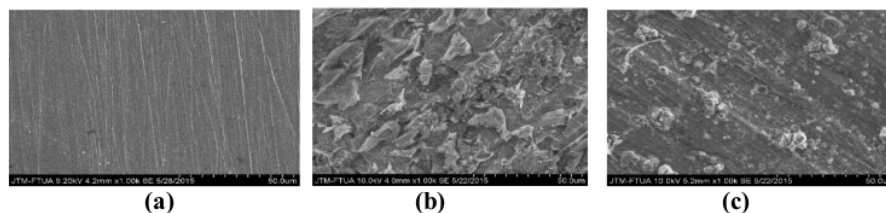

(a) (b) (c)  
**Figure 7.** St 37 S surface morphology (a) without (b) and with immersion in HCl and (c) immersion in HCl containing 0,5% SLE, with a 100 X magnification.

## Conclusions

According to the findings, SLE can be employed as a corrosion inhibitor. IE(%) was 67% percent for tests based on WL, and 69.72% for measurements based on PDP, at the optimum extract C of 0.8% in 1 N HCl.  $I_{\text{corr}}$  decreased with SLE increasing C, according to the PDP study. The  $E_a$  value increased with higher SLE C, indicating that corrosion was more difficult to achieve. SEM results also revealed a significant difference in IE(%) without and with SLE.

## Authors' contributions

**L. Anggraini:** conceived and designed the analysis; wrote the paper. **Emriadi:** conceived and designed the analysis; performed the analysis; wrote the paper. **Y. Stiadi:** collected the data; inserted data or analysis tools; performed the analysis. **S. Zulaiha:** inserted data or analysis tools; performed the analysis. **H. Pardi:** inserted data or analysis tools; performed the analysis; wrote the paper.

## Abbreviations

**1/T:** first-order reaction  
**AE:** auxiliary electrode  
**C:** concentration  
**C/θ:** concentration per degree of closure  
**CH<sub>3</sub>OH:** methanol  
**CHCl<sub>3</sub>:** chloroform  
**CR:** corrosion rate  
**E:** electric potential  
**E<sub>corr</sub>:** corrosion potential  
**FeCl<sub>3</sub>:** ferric chloride  
**FTIR:** Fourier transform infrared spectroscopy  
**H<sub>2</sub>SO<sub>4</sub>:** sulfuric acid  
**HCl:** hydrochloric acid  
**I:** electric current  
**I<sub>corr</sub>:** corrosion current density  
**IE%:** inhibition efficiency  
**KBr:** potassium bromide  
**ln V:** reactant velocity  
**m<sub>1</sub>:** initial weight  
**m<sub>2</sub>:** final weight  
**MS:** mild steel  
**NH<sub>3</sub>:** ammonia  
**PDP:** potentiodynamic polarization  
**R:** reaction rate  
**R<sup>2</sup>:** correlation coefficient

**RE:** reference electrode  
**SEM:** scanning electron microscopy  
**SLE:** Senggani (*Melastoma candidum* D. Don) leaf extract  
**St-37 S:** stainless steel 37  
**T:** temperature  
**WE:** working electrode  
**WL:** weight loss

#### **Symbols definition**

**$\Delta G$ :** free enthalpy  
 **$\Delta H^\circ$ :** enthalpy  
 **$\Delta G_{\text{ads}}$ :** Gibb's free energy of adsorption  
 **$\Delta S^\circ$ :** entropy  
 **$E_a$ :** activation energy  
 **$K_{\text{ads}}$ :** adsorption equilibrium constant ( $\text{L}/\text{mg}^{-1}$ )

#### **References**

1. Kumpawat N, Chaturvedi A, Upadhyay RK. Corrosion Inhibitor of Mild Steel by Alkaloid Extract of *Ocimum sanctum* in HCl and HNO<sub>3</sub> Solutions. *Res J Chem. Sci.* 2012;2:51-56.
2. Praveen BM, Venkatesha TV. Metol as Corrosion Inhibitor for Steel. *Int J Electrochem Sci.* 2009;4:267-275.
3. Eddy NO, Awe F, Ebenso EE. Adsorption and Inhibitive Properties of Ethanol Extracts of Leaves of *Solanum Melongena* for the Corrosion of Mild Steel in 0.1 M HCl. *Int J Electrochem Sci.* 2010;5:1996-2011.
4. Ferdosi HM, Tavakoli H. Electrochemical properties of a new green corrosion inhibitor derived from *Prosopis farcta* for St37 steel in 1 M hydrochloric acid. *Met Mat Int.* 2020;26:654-1663. <https://doi.org/10.1007/s12540-019-00453-6>
5. Jafari H, Akbarzade K, Danaee I. Corrosion inhibition of carbon steel immersed in a 1 M HCl solution using benzothiazole derivatives. *Arab J Chem.* 2019;12:1387-1394. <https://doi.org/10.1016/j.arabjc.2014.11.018>
6. Heragh MF, Tavakoli H. Synergetic effect of the combination of *Prosopis Farcta* extract with sodium dodecyl sulfate on corrosion inhibition of St37 steel in 1 M HCl medium. *J Molec Struc.* 2021;245:131086. <https://doi.org/10.1016/j.molstruc.2021.131086>
7. Obralić E, Čatić S, Odobašić A et al. Corrosion Inhibition of Pektin C on St-34 in Hydrochloric Acid. *Technol Acta: Sci/Prof J Chem Technol.* 2021;14:7-10. <https://doi.org/10.5281/zenodo.5520552>
8. Öztürk S, Gerengi H, Solomon MM et al. A newly synthesized ionic liquid as an effective corrosion inhibitor for carbon steel in HCl medium: combined experimental and computational studies. *Mat Today Commun.* 2021:102905. <https://doi.org/10.1016/j.mtcomm.2021.102905>
9. Lahbib H, Ben HS, Gerengi H et al. Corrosion inhibition performance of dwarf palm and *Cynara cardunculus* leaves extract for St37 steel in 15% H<sub>2</sub>SO<sub>4</sub>: a comparative study. *J Adhes Sci Technol.* 2021;35:691-722. <https://doi.org/10.1080/01694243.2020.1819701>

10. Singh A, Ansari KR, Banerjee P et al. Corrosion inhibition behavior of piperidinium based ionic liquids on Q235 steel in a hydrochloric acid solution: Experimental, density functional theory and molecular dynamics study. *Coll Surf A: Physicochem Eng Asp.* 2021;623:126708. <https://doi.org/10.1016/j.colsurfa.2021.126708>
11. Chauhan DS, Mazumder MJ, Quraishi MA et al. Chitosan-cinnamaldehyde Schiff base: a bioinspired macromolecule as corrosion inhibitor for oil and gas industry. *Int J Bio Macromol.* 2021;158:127-138. <https://doi.org/10.1016/j.ijbiomac.2020.04.200>
12. Quraishi MA, Ansari KR, Chauhan DS et al. Vanillin modified chitosan as a new bioinspired corrosion inhibitor for carbon steel in oil-well acidizing relevant to petroleum industry. *Cellulose.* 2020;27:6425-6443. <https://doi.org/10.1007/s10570-020-03239-x>
13. Solomon MM, Gerengi H, Kaya T et al. Enhanced corrosion inhibition effect of chitosan for St37 in a 15% H<sub>2</sub>SO<sub>4</sub> environment by silver nanoparticles. *Int J Bio Macromolec.* 2017;104:638-649. <https://doi.org/10.1016/j.ijbiomac.2017.06.072>
14. Gerengi H, Solomon MM, Öztürk S et al. Evaluation of the corrosion inhibiting efficacy of a newly synthesized nitron against St37 steel corrosion in an acidic medium: experimental and theoretical approaches. *Mat Sci Eng: C.* 2018;93:539553. <https://doi.org/10.1016/j.msec.2018.08.031>
15. Yildiz M, Gerengi H, Solomon MM et al. Influence of 1-butyl-1-methylpiperidinium tetrafluoroborate on St37 steel dissolution behavior in a HCl environment. *Chem Eng Commun.* 2018;205:538-548. <https://doi.org/10.1080/00986445.2017.1407759>
16. Deswati, Hilfi P, Hamzar S et al. Adsorptive Stripping Voltammetry for the Simultaneous Determination of Cd, Cu, Cr, and Pb in Water Samples Using Fluorexon: An Optimization Single Factor. *Analyt Bioanalyt Electrochem.* 2018;10:1491-1505.
17. Deswati, Hamzar S, Izzati R et al. Application of Central Composite Design Optimization Technique for Determination of Copper in Fruit and Vegetable Samples with Adsorptive Stripping Voltammetry in the Presence of Calcein. *Rasayan J Chem.* 2017;10:1359-1367. <https://doi.org/10.7324/RJC.2017.1041810>
18. Deswati, Suyani H et al. Simultaneous Determination of Cu, Pb, Cd, and Zn In Tap Water Samples in the Presence of Alizarin: Differential Pulse Adsorptive Stripping Voltammetry. *Analyt Bioanalyt Electrochem.* 2017;9(8):969-981.
19. Deswati, Hamzar Suyani, Rahmiana Zein et al. Adsorptive Stripping Voltammetric Method For The Individual Determination Of Cd(II), Cu(II), Pb(II), and Zn(II) in Vegetable Samples using Calcein. *Rasayan J Chem.* 2017;10(2):549-557.
20. Deswati, Pardi H, Suyani H et al. Adsorptive Cathodic Stripping Voltammetric Method with Alizarin for the Simultaneous Determination of Cadmium, and Zinc in Water Samples. *Orient J Chem.* 2016; 32(6): 3071-3079.
21. Deswati, Pardi H, Suyani H et al. 2016. The Development Method for a Sensitive Simultaneous Determination of Pb (II), Cd (II) and Zn (II) by Adsorptive Cathodic Stripping Voltammetry Using Alizarin as a Complexing Agent. *Analyt Bioanalyt Electrochem.* 2016; 8(7): 885-898.
22. Deswati, Suyani H, Zein R et al. Applicability of calcein as a chelating agent for simultaneous determination of Cd (II), Cu (II), Pb (II) and Zn (II) in water samples by adsorptive stripping voltammetry. *J Chem Phar Res.* 2015; 7(10): 833-840.

23. Pardi H, Deswati D, Edelwis TW et al. Differential pulse adsorptive cathodic stripping voltammetry for the simultaneous determination of pb and zn in seawater using calcon. *Port Electrochim Acta*. 2021;39(1):45-57.
24. Pardi H, Deswati D, Suyani H et al. Cathodic Stripping Voltammetric Determination of Essential Element (Copper and Zinc) in Drinking Water. *Analyt Bioanalyt Electrochem*. 2019;11(6):691-702.
25. Deswati, Munaf E, Suyani H et al. Simultaneous determination of trace amounts of iron, cobalt, nickel and chromium in water samples with calcon as complexing agent by adsorptive stripping voltammetry. *Asian J Chem*. 2015; 27(11): 3978-3982.
26. Rbaa M, Galai M, Abousalem AS et al. Synthetic, spectroscopic characterization, empirical and theoretical investigations on the corrosion inhibition characteristics of mild steel in molar hydrochloric acid by three novel 8-hydroxyquinoline derivatives. *Ionics*. 2020;26:503-522. <https://doi.org/10.1007/s11581-019-03160-9>
27. Solomon MM, Gerengi H, Umoren SA. Carboxymethyl cellulose/silver nanoparticles composite: synthesis, characterization and application as a benign corrosion inhibitor for St37 steel in a 15% H2SO4 medium. *ACS Appl Mat Interfac*. 2017;9:6376-6389. <https://doi.org/10.1021/acsami.6b14153>
28. Jacob KS, Parameswaran G. Corrosion inhibition of mild steel in a hydrochloric acid solution by Schiff base furoin thiosemicarbazone. *Corros Sci*. 2010;52(1):224-228. <https://doi.org/10.1016/j.corsci.2009.09.007>
29. Quraishi MA, Singh A, Singh VK et al. Green approach to corrosion inhibition of mild steel in hydrochloric acid and sulphuric acid solutions by the extract of *Murraya koenigii* leaves. *Mat Chem Phys*. 2010;122:114-122. <https://doi.org/10.1016/j.matchemphys.2010.02.066>
30. Shainy KM, Ammal PR, Unni KN et al. Surface interaction and corrosion inhibition of mild steel in hydrochloric acid using pyoverdine, an eco-friendly bio-molecule. *J Bio Tribo-Corros*. 2016;2:1-12. <https://doi.org/10.1007/s40735-016-0050-3>
31. Masna AE, Hermansyah A, Hilf P. The Extract of Waru (*Hibiscus Tiliaceus* L.) Leaf as an Environment-Friendly Corrosion Inhibitor of Mild Steel in a 1 N Hydrochloric Acid Medium. *Pollution Research*. 2019;38, 544-550.
32. Deswati, Suyani H, Safni S et al. Simultaneous determination of cadmium, copper and lead in sea water by adsorptive stripping voltammetry in the presence of calcon as a complexing agent. *Indon J Chem*. 2013;13(3): 236-241.
33. Deswati A, Munaf E, Suyani H et al. The sensitive and simple determination of trace metals Fe, Co, Ni and Cr in water samples by adsorptive stripping voltammetry (AdSV) in the presence of calcon. *Res J Phar Bio Chem Sci*. 2014; 5(4): 990-1000
34. Deswati, Suyani H, Rahmi I et al. Optimization for the Simultaneous Determination of Zinc in Environmental Samples With Calcon by Adsorptive Stripping Voltammetry: Response Surface Methodology. *Orient J Chem*. 2017;33(4):2060-2070.

## ORIGINALITY REPORT

13%

SIMILARITY INDEX

6%

INTERNET SOURCES

10%

PUBLICATIONS

4%

STUDENT PAPERS

## PRIMARY SOURCES

- 
- |   |  |     |
|---|--|-----|
| 1 | Submitted to University of Liverpool<br>Student Paper  | 1 % |
| 2 | Anti-Corrosion Methods and Materials,<br>Volume 60, Issue 1 (2013-01-05)<br>Publication  | 1 % |
| 3 | <a href="http://www.smujo.id">www.smujo.id</a><br>Internet Source  | 1 % |
| 4 | Bhuvaneshwari T. K., Jeyaprabha C., Arulmathi P.. " Corrosion inhibition of mild steel in hydrochloric acid by leaves extract of ",<br>Journal of Adhesion Science and Technology,<br>2020<br>Publication                                  | 1 % |
| 5 | Lutz Bornmann, Richard Williams. "Can the journal impact factor be used as a criterion for the selection of junior researchers? A large-scale empirical study based on ResearcherID data", Journal of Informetrics,<br>2017<br>Publication | 1 % |
-

6	<p>Hana Lahbib, Samia Ben Hassen, Hüsnü Gerengi, Marziya Rizvi, Yasser Ben Amor. "Corrosion inhibition performance of dwarf palm and leaves extract for St37 steel in 15% H<sub>2</sub>SO<sub>4</sub>: a comparative study", Journal of Adhesion Science and Technology, 2020</p> <p>Publication</p>	1 %
7	<p>"Polymeric Corrosion Inhibitors for Greening the Chemical and Petrochemical Industry", Wiley, 2022</p> <p>Publication</p>	1 %
8	<p>B. M. Praveen, B. M. Prasanna, Narayana Hebbar, P. Shivakeshava Kumar, M. R. Jagadeesh. "Experimental and Theoretical Studies on Inhibition Effect of the Praziquantel on Mild Steel Corrosion in 1M HCl", Journal of Bio- and Tribo-Corrosion, 2018</p> <p>Publication</p>	1 %
9	<p>Submitted to Universitas Muhammadiyah Ponorogo</p> <p>Student Paper</p>	<1 %
10	<p><a href="http://www.tandfonline.com">www.tandfonline.com</a></p> <p>Internet Source</p>	<1 %
11	<p>A. Dandia, S. L. Gupta, P. Singh, M. A. Quraishi. " Ultrasound-Assisted Synthesis of Pyrazolo[3,4- ]pyridines as Potential Corrosion</p>	<1 %

# Inhibitors for Mild Steel in 1.0 M HCl ", ACS Sustainable Chemistry & Engineering, 2013

Publication

12

[utpedia.utp.edu.my](http://utpedia.utp.edu.my)

Internet Source

<1 %

13

Submitted to State Islamic University of Alauddin Makassar

Student Paper

<1 %

14

[eprints.utm.my](http://eprints.utm.my)

Internet Source

<1 %

15

[ijmm.ir](http://ijmm.ir)

Internet Source

<1 %

16

[scielo.pt](http://scielo.pt)

Internet Source

<1 %

17

Ahmed A. Fadhil, Anees A. Khadom, Salima K. Ahmed, Hongfang Liu, Chaoyang Fu, Hameed B. Mahood. "Portulaca grandiflora as new green corrosion inhibitor for mild steel protection in hydrochloric acid: Quantitative, electrochemical, surface and spectroscopic investigations", Surfaces and Interfaces, 2020

Publication

<1 %

18

Li Huang, Kun-Peng Yang, Qing Zhao, Hui-Jing Li, Jin-Yi Wang, Yan-Chao Wu. "Corrosion resistance and antibacterial activity of procyanidin B2 as a novel environment-

<1 %



friendly inhibitor for Q235 steel in 1M HCl solution", Bioelectrochemistry, 2022

Publication

---

19

Mohammad Mobin, Irfan Ahmad, Manilal Murmu, Priyabrata Banerjee, Ruby Aslam. "Corrosion inhibiting properties of polysaccharide extracted from Lepidium meyenii root for mild steel in acidic medium: Experimental, density functional theory, and Monte Carlo simulation studies", Journal of Physics and Chemistry of Solids, 2023

Publication

---

20

Bozorg, Mansoor, taghi shahrabi farahani, jaber neshati, zahra chaghazardi, and Ghodsi mohammadi. "Myrtus Communis as green inhibitor of copper corrosion in Sulphuric Acid", Industrial & Engineering Chemistry Research, 2014.

Publication

---

21

Ebrahim Kamali Ardakani, Elaheh Kowsari, Ali Ehsani, Seeram Ramakrishna. "Performance of all ionic liquids as the eco-friendly and sustainable compounds in inhibiting corrosion in various media: A comprehensive review", Microchemical Journal, 2021

Publication

---

22

Nkem B. Iroha, Cordelia U. Dueke-Eze. "Experimental Studies on Two

<1 %

<1 %

<1 %

<1 %

Isonicotinohydrazide-Based Schiff Bases as New and Efficient Inhibitors for Pipeline Steel Erosion Corrosion in Acidic Cleaning Solution", Chemistry Africa, 2021

Publication

23

Sappani Hari Kumar, Sambantham Karthikeyan. "Torsemide and Furosemide as Green Inhibitors for the Corrosion of Mild Steel in Hydrochloric Acid Medium", Industrial & Engineering Chemistry Research, 2013

Publication

<1 %

24

Serkan Öztürk, Nuray Altınölçek. "Synthesis of tri - cationic surfactants containing two amide functional groups and inhibition effectiveness against metal corrosion in acidic medium", Journal of Surfactants and Detergents, 2022

Publication

<1 %

25

Xiaoyun Zhang, Yunxiang Zheng, Xiangpeng Wang, Yufeng Yan, Wei Wu. "Corrosion Inhibition of N80 Steel Using Novel Diquaternary Ammonium Salts in 15% Hydrochloric Acid", Industrial & Engineering Chemistry Research, 2014

Publication

<1 %

26

[archive2.covenantuniversity.edu.ng](https://archive2.covenantuniversity.edu.ng)

Internet Source

<1 %

27

[scholar.lib.vt.edu](https://scholar.lib.vt.edu)

Internet Source

<1 %

28

[www.elixirpublishers.com](http://www.elixirpublishers.com)

Internet Source

&lt;1 %

29

Giangiaco­mo Bravo, Mike Farjam, Francisco Grimaldo Moreno, Aliaksandr Birukou, Flaminio Squazzoni. "Hidden connections: Network effects on editorial decisions in four computer science journals", Journal of Informetrics, 2018

Publication

&lt;1 %

30

Liangyuan Chen, Dongzhu Lu, Yanhu Zhang. "Organic Compounds as Corrosion Inhibitors for Carbon Steel in HCl Solution: A Comprehensive Review", Materials, 2022

Publication

&lt;1 %

31

N. Gunavathy, S. C. Murugavel. " Corrosion Inhibition Studies of Mild Steel in Acid Medium Using Fruit Peel Extract ", E-Journal of Chemistry, 2012

Publication

&lt;1 %

Exclude quotes  OnExclude matches  OffExclude bibliography  On